arXiv:cond-mat/0507081v2 [cond-mat.supr-con] 5 Jul 2005

^{23}Na NMR Study of Layered Superconductor $Na_xCoO_2 \cdot yH_2O$

H.Ohta [a,*], C.Michioka [a], Y.Itoh [a], K.Yoshimura [a], H.Sakurai [b], E.Takayama-Muromachi [b], K.Takada [c], T.Sasaki [c]

[a] *Department of Chemistry, Graduate School of Science, Kyoto University, Kyoto 606-8502, Japan*
[b] *Superconducting Materials Center, NIMS, Namiki, Tsukuba, Ibaraki, 305-0044, Japan*
[c] *Advanced Materials Laboratry, NIMS, Namiki, Tsukuba, Ibaraki, 305-0044, Japan*

Abstract

We measured ^{23}Na-NMR spectra and nuclear spin-lattice relaxation rates $^{23}(1/T_1)$ of superconducting and non-superconducting *bi*layer hydrate $Na_xCoO_2 \cdot yH_2O$ ($x \sim 0.3, y \sim 1.3$). The central resonance frequency shows a small but various shift due to the difference in the shielding effect by intercalated H_2O molecules. The different shielding effect also gives a large difference in the magnitude of $^{23}(1/T_1)$.

Key words: Sodium cobalt oxide, Superconductivity, ^{23}Na-NMR
PACS: 71.10.Hf; 71.27.+a; 75.30Mb

Recently, a number of investigations for the superconductivity in *bi*layer hydrate (BLH) sodium cobalt oxide $Na_xCoO_2 \cdot yH_2O$ ($x \sim 0.3, y \sim 1.3$) have been done. Different properties were reported especially in NMR studies for different samples. In a report of chemical study, it is emphasized that some Na^+ ions are exchanged by H_3O^+ ions during intercalation of H_2O molecules[1]. Because of the nonstoichiometric properties in BLH, i. e. ambiguities of the amount of Na^+, H_2O, and H_3O^+, similar samples are hardly obtained. More chemical studies are needed to clarify the origin of the magnetism and the superconductivity of BLH.

We prepared two BLH samples by following processes[2]. Powders of Co_3O_4 and Na_2CO_3 were well mixed and heated at 800 °C for 20 hours in O_2 atmosphere. The obtained powder sample was characterized as in a single phase of $Na_{0.7}CoO_2$ by powder X-ray diffraction (XRD) measurements. Then $Na_{0.7}CoO_2$ was immersed in Br_2/CH_3CN solution for several days to deintercalate Na ions. The dried powder was immersed in distilled water for 1 day. The water-intercalated powder was put in a sealed chamber filled with 75 % of relative humidity (RH). We prepared several samples by changing the duration kept in the chamber, and frozen at about - 10 °C for quenching further change. A sample named BLH1 was kept for one week in 75 % RH atmosphere, and BLH2 for 1 month.

Another two samples named BLHs1 and BLHs2 were synthesized by similar process, but not at the same time with BLH1 and BLH2. BLHs1 has already been studied in [3]. BLHs2 was a derivative of BLHs1 after about 1 year in the 75 % RH atmosphere before frozen.

Each sample was characterized to be in a single phase of the BLH by powder XRD result. The lattice constant c of BLHs1 and BLHs2 estimated by the XRD results are smaller than that of BLH1 and BLH2. This difference in c indicates that the content of H_3O^+ is different between two groups. The superconducting transition temperature T_c estimated by magnetization measurements was $T_c < 1.8$ K for BLH1 and ~ 4.5 K for BLH2; $T_c \sim 4.7$ K for BLHs1 and ~ 3 K for BLHs2.

We observed the free induction decay (FID) signals of ^{23}Na nuclei ($I = 3/2$) by NMR at 7.485 T. The Fourier transformed NMR spectra of FID signals are shown in Fig. 1. Here, ν_{ref} denotes the resonance fre-

* Corresponding author. Tel: +81-75-753-3990 fax: +81-75-753-4000
Email address: shioshio@kuchem.kyoto-u.ac.jp (H.Ohta).

quency of ^{23}Na nuclei in NaCl aqueous solution at room temperature ($\nu_{\rm ref}$ = 84.287 MHz). The satellite lines due to the nuclear quadrupole interaction may wipe out. The shift of peak resonance is very small compared with $Na_{0.7}CoO_2$ ($\nu - \nu_{\rm ref} \sim 40$ kHz)[4], and the temperature dependence of the shift is also small, suggesting a weak Co-O-Na coupling.

The recovery curves of FID signals were measured by inversion recovery method for obtaining ^{23}Na nuclear spin-lattice relaxation rate $^{23}(1/T_1)$. The temperature dependence of $^{23}(1/T_1)$ is shown in Fig. 2. The relaxation rate was estimated by the least-square fitting using the theoretical function of the central transition ($I_z = 1/2 \leftrightarrow -1/2$). While the peak shift is small and similar in each BLH as shown in Fig. 1, the absolute value of $^{23}(1/T_1)$ is markedly different. A broad peak around 100 $\sim$ 150 K in each $^{23}(1/T_1)$ and a rapid increase above 200 K except for BLHs2 are observed. This rapid increase in $^{23}(1/T_1)$ may originate in the motion of Na ions[5].

The magnitude of $^{23}(1/T_1)$ of BLH is on two or three order smaller than that of $Na_{0.7}CoO_2$[5,6]. If the hyperfine coupling of BLH is on two or three order smaller than that of $Na_{0.7}CoO_2$[4], the shift should be 0.05 $\sim$ 0.5 kHz. The hyperfine coupling is thought to be shielded by the intercalated H_2O molecules. The difference in $^{23}(1/T_1)$ may be attributed to the difference of compositions of H_2O, H_3O^+, and Na^+, which may cause the different surroundings around a sodium ion. Since $1/T_1$ becomes slower with increasing the duration, the shielding effect is enhanced by the time duration in the chamber. We note that ^{59}Co and ^{17}O-NMR/NQR are hard to probe these difference of compositions, because Co and O nuclei are in the CoO_2 plane and outside of the layer consisting of the nonstoichiometric components. Therefore, ^{23}Na-NMR should be a strong probe to elucidate the physical properties of the BLH.

In conclusion, we measured ^{23}Na-NMR in *bi*layer hydrate sodium cobalt oxides, including nonsuperconducting *bi*layer hydrate. At the Na site, the hyperfine coupling is weakened by the intercalated H_2O molecules, and the nuclear spin-lattice relaxation shows a large difference in four samples with different superconducting temperatures.

Acknowledgement This study was supported in part by Grants-in Aid for Scientific Research from Japan Society for the Promotion of Science (16076210).

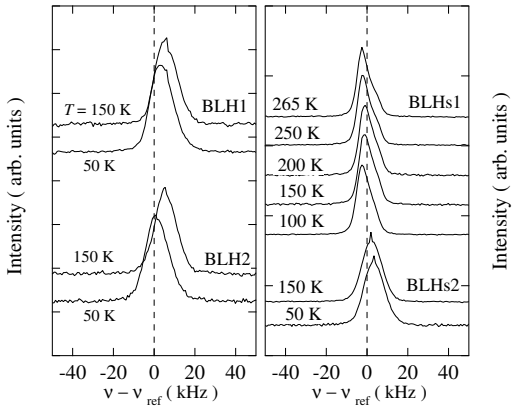

Fig. 1. ^{23}Na-NMR spectra of BLH1,2 and BLHs1,s2. $\nu_{\rm ref}$ is the resonance frequency of ^{23}Na in NaCl aqueous solution at room temperature ($\nu_{\rm ref}$ = 84.287 MHz). No satellite lines were observed.

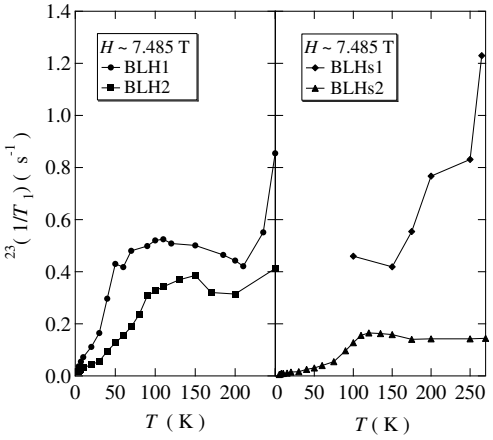

Fig. 2. Temperature dependence of $^{23}(1/T_1)$.

References

[1] K. Takada *et al*, J. Mater. Chem. **14** (2004) 1448.

[2] K.Takada *et al*, Nature **422** (2003) 53.

[3] M. Kato *et al*, Physica B **359-361** (2005) 482.

[4] I. R. Mukhamedshin *et al*, Phys. Rev. Lett. **93** (2004) 167601.

[5] J. L. Gavilano *et al*, Phys. Rev. B **69** (2004) 100404(R).

[6] Y. Ihara *et al*, J. Phys. Soc. Jpn **73** (2004) 2963.